

Intertek Polychemlab
Koolwaterstofstraat 1
6161 RA Geleen
The Netherlands

Telephone: +31 (0)88 126 8888

www.intertek.com


TEST REPORT – RE36136-3A

TESTING 3 SAMPLES OF PP AND 3 SAMPLES OF RPP.

SAMPLE 3 INPUT 2021 PP SAMPLE AND SAMPLE 3 OUTPUT 2021 PP SAMPLE

Intertek MSG

Attn. James Lynch
Room D135 The Wilton Centre
TS10 4RF Redcar
United Kingdom

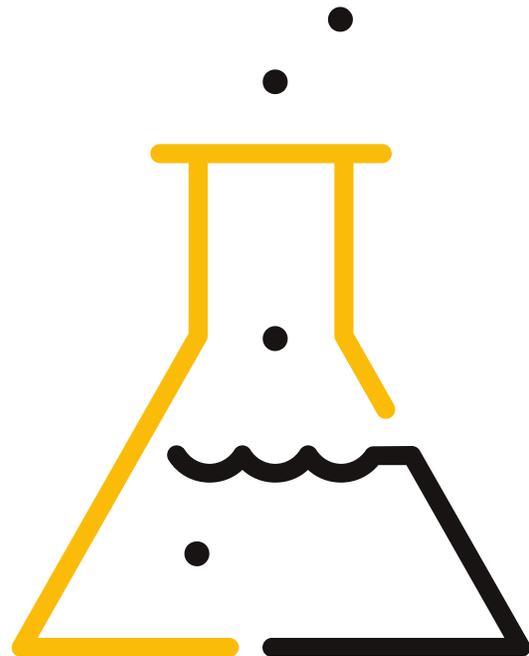

DATE

September 1st, 2021

This test report, including front-page and attachments, shall not be reproduced except in full, without written approval of Intertek Polychemlab B.V.
This version replaces all previous versions



RE36136-3A

September 1st, 2021

RE26136-3A: This version replaces all previous versions.

Reason for revision: Addition of results re-analysis xylene extractables.

Dear Mr. Lynch,

Hereby we present to you the results of the laboratory study, which was carried out by your request (Ref. SO36136).

The general conditions of delivery of Intertek Polychemlab B.V., located in Geleen, the Netherlands, are applicable. These conditions are an integral part of all research carried out and the services and consultations provided; where appropriate, expanded upon by agreements specific to the client.

Samples of unknown origin can only be checked for plausibility to a limited extent. Results of the examination of these samples only relate to the samples as received by Intertek.

Intertek is not responsible for the data supplied by the client. These data may affect the validity of the analysis results.

If information about the measurement uncertainty of a method is required, this can be provided on request.

We trust that this information will meet your approval.

Yours sincerely,


Intertek Polychemlab B.V.



Rens Pörteners
Application Specialist Food Contact



Frans Jongen
Application Specialist Technique

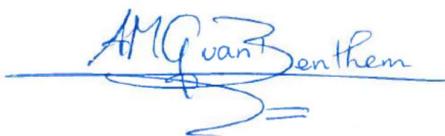

Drs. Gabriëlle van Benthem
Application Specialist Food Contact

This test report, including front-page and attachments, shall not be reproduced except in full, without written approval of Intertek Polychemlab B.V.
This version replaces all previous versions.

RE36136-3A

September 1st, 2021

1	Introduction	4
2	SAMPLES	4
2.1	Description of samples	4
3	Method(s) applied	5
3.1	Screening of volatiles, non-volatiles, and additives	5
3.1.1	Screening of volatile organic compounds – TD GC-MS	5
3.1.2	Screening of residual additives and non-volatiles – LC-MS	5
3.2	Phthalates screening	6
3.3	Metal screening (ICP/MS, FIMS): screening multi-elements	7
3.3.1	Sample preparation	7
3.3.2	Hg-analyzer (FIMS)	7
3.3.3	ICP-MS analysis	7
3.3.4	ICP-OES analysis	7
3.4	CFR 177.1520 (final products) samples	8
3.4.1	n-Hexane extraction test according to 21 CFR section 177.1520	8
3.4.2	Xylene soluble fraction test according to 21 CFR section 177.1520	8
4	Results and discussion	9
4.1	TD GC-MS screening - volatiles	9
4.2	LC-MS screening – non-volatiles and additives	9
4.3	Phthalates screening	11
4.3	Metal screening (ICP/MS, FIMS): screening multi-elements	12
4.4	CFR 177.1520 (final products) samples	13
4.4.1	Maximum extractable fraction in n-hexane	13
4.4.2	Maximum soluble fraction in xylene	13
	Appendix I: Results and chromatograms of TD GC-MS screening	14
	Appendix II: Results and chromatograms of LC-MS screening	21



RE36136-3A

September 1st, 2021

1 INTRODUCTION

Intertek MSG requested Intertek Polychemlab B.V. to perform the following analysis on 3 PP samples (feedstock) and 3 rPP samples (final products) to determine the difference between the samples before and after recycling:

- GC/MS analysis for volatile organic compounds;
- Additive Screening;
- LC/MS for non-volatiles;
- Determination of Phthalates;
- Determination of Metals;
- FDA extraction testing (21 CFR 177.1520) – 3 samples – only on final products.

2 SAMPLES

2.1 Description of samples

The samples were described by the client as displayed in table 1. After arrival the samples were registered and coded with a unique Intertek LIMS number.

Table 1: Sample description

NO.	INTERTEK SAMPLE DESCRIPTION	CUSTOMER SAMPLE DESCRIPTION	DATE RECEIVED	INTERTEK LIMS NUMBER
1	Sample 1 input	Sample 1 input 2019 PP Sample	May 12 th , 2021	23163596
2	Sample 1 output	Sample 1 output 2019 rPP Sample (30% with virgin PP)	May 12 th , 2021	23163597
3	Sample 2 input	Sample 2 Input 2020 PP Sample	May 12 th , 2021	23163598
4	Sample 2 output	Sample 2 output 2020 rPP Sample	May 12 th , 2021	23163599
5	Sample 3 input	Sample 3 input 2021 PP ptt	July 13th, 2021	23183912
6	Sample 3 output	Sample 3: 22 hr refresh output material 20-21 trial	July 13th, 2021	23183913

Remark: This report holds the results of sample 5 and 6. The results of the other samples are reported respectively in RE36136-1 and RE36136-2.



RE36136-3A

September 1st, 2021

3 METHOD(S) APPLIED

3.1 Screening of volatiles, non-volatiles, and additives

3.1.1 Screening of volatile organic compounds – TD GC-MS

The volatile compounds from the samples were analyzed by thermal desorption TD GC-MS. This analysis was performed on the sample after rinsing to pH neutral (only Input) and cryogenic grinding.

Concentrations were semi-quantitatively determined using an external standard of toluene as a reference compound. The details of the method applied can be found in table 2. For the analysis, a single run was performed.

Table 2: Method applied for the volatile compounds analysis

GC	AGILENT 7890B
Detector:	Agilent 5977B Mass detector
Thermal desorption unit:	Unity xR
Software:	Mass hunter GC-MS acquisition B.07.04.2260
Column:	Restek 624 Sil-MS – 60m x 320 µm x 1.8 µm
Temperature program:	Initial 32°C, hold for 5 min, ramp 10°C/min until 280°C, hold for 10 min.
Detection:	3 min, 29 – 350 AMU
Desorption temperature:	110°C
Desorption time:	30 min

3.1.2 Screening of residual additives and non-volatiles – LC-MS

The analysis of non-volatile components from the sample was performed using LC-MS technique. An in-house method developed for the reference compounds, which are common to expect from the polymers such as polyolefins (mentioned below) were analyzed. The samples (~0.3g) were dissolved in 10 mL boiling toluene, quenched with 20 mL methanol, and concentrated 10 times prior to injection. For the analysis, a single run was performed.

Each reference standard mentioned below was used to quantify the corresponding components in the measurement solution if any detected. Please note that unknown substances cannot be identified with this technique, only mass/fragment ions information is provided. The details of the method applied can be found in table 3.

Reference compounds: *Benzophenone, oleamide, erucamide, hexadecanoic acid, octadecanoic acid, Atmer 163, Irgacure 184, Irgafos 168, Irgafos 168 phosphate, Irganox 245, Irganox PS800, Irganox PS802, Irganox 1010, Irganox 1076, Irganox 1330 and Irganox 3114.*



RE36136-3A

September 1st, 2021

Table 3: Method applied for the LC-MS screening

LC	WATERS ACQUITY H CLASS
Detector	Waters SQ Detector 2
Software	MassLynx V4.1
Column	Waters Acquity UPLC BEH Phenyl, 2.1 x 100mm, 1.7 µm
Column temperature	40°C
Injection	2 µl
Mobile phase A	0.1% formic acid in water
Mobile phase B	Methanol
Mobile phase C	Isopropanol
Gradient	From 20% A, 70% B and 10% C to 90% and 10% C B within 6 min, hold for 1 min.
Flow	0.4 ml/min
MS-screening	<i>m/z</i> 100-2000 ESI in positive, <i>m/z</i> 60-2000 ESI negative mode For some targeted components APCI was used

3.2 Phthalates screening

Approximately 0.5 gram was cryogenically grinded and extracted for 4 hours using methylene chloride. The extracts were evaporated to dryness and redissolved in methanol (1:1). For the analysis, a single run was performed. The following phthalates were quantified using external standards using LC-MS/MS:

- 2-Ethylhexyl methyl terephthalate (EHMTP);
- Bis(2-ethyl hexyl) phthalate (DEHP);
- Diisononyl phthalate (DINP);
- Butylbenzyl phthalate (BBP);
- Dibutyl phthalate (DBP);
- Diethyl phthalate (DEP);
- Diisobutyl phthalate (DIBP);
- Dimethyl phthalate (DMP);
- Di-n-hexylphthalate (DNHP);
- Dipentyl phthalate (DPP);
- Di-isohexyl phthalate (DIHxP);
- Di n octyl phthalate (DnOP);
- Dinonyl phthalate (DNP);
- Diisopentyl phthalate (DIPP);
- Diisodecyl phthalate (DIDP).

The apparatus and settings used are mentioned in table 4.

Table 4: LC-MS/MS settings for phthalates analysis

UPLC	SCIEX EXIONLCTM
Detector	Sciex QTRAP 4500
Software	Analyst 1.7, MultiQuant 3.0.3
Analytical Column	Waters Acquity CSH C18 column 100*2.1 mm, 1.7 µm,
Guardcolumn	Waters Isolator Column 2.1x50mm



RE36136-3A

September 1st, 2021

3.3 Metal screening (ICP/MS, FIMS): screening multi-elements

3.3.1 Sample preparation

Samples were digested with concentrated oxidizing acid at elevated temperature and pressure with a microwave. After digestion, the solutions were transferred into a volumetric flask and analyzed with ICP-MS and FIMS. For the analysis, a single run was performed.

3.3.2 Hg-analyzer (FIMS)

Mercury was analysed using a "Perkin Elmer FIMS100; Flow Injection Mercury System".

3.3.3 ICP-MS analysis

The apparatus and settings used for the ICP-MS analysis is mentioned in table 5, and the results of the performed suitability test is mentioned in table 6.

Table 5: Method applied for the ICP-MS analysis

APPARATUS	PERKIN ELMER NEXION 350D EQUIPPED WITH PREPFAST SAMPLE INTRODUCTION SYSTEM
Mode	Standard/KED
Plasma Flow (l/min)	18
Aux. Flow (l/min)	1.2
Neb. Flow (l/min)	0.97
RF Power (Watt)	1600

Table 6: ICP-MS System Suitability test

ANALYTE	UNIT	SPECIFICATION	DAILY
Be	Counts	> 2000	3496
In	Counts	> 40000	70820
U	Counts	> 30000	47474
CeO/Ce	%	≤ 2.5	1.36
Ce ⁺⁺ /Ce	%	≤ 3.0	1.24
Background (220)	Counts	<1	2

3.3.4 ICP-OES analysis

The apparatus and setting used for the ICP-OES analysis is mentioned in table 7, and the results of the performed suitability test is mentioned in table 8.



RE36136-3A

September 1st, 2021

Table 7: Method applied for the ICP-OES analysis

APPARATUS	PERKIN-ELMER OPTIMA 8300DV SUPPLIED WITH FAST-LOOP SAMPLE INTRODUCTION SYSTEM
Plasma View	Axial
Plasma Flow (l/min)	10
Aux. Flow (l/min)	0.2
Neb. Flow (l/min)	0.70
RF Power (Watt)	1350

Table 8: ICP-OES System Suitability test

ANALYTE	UNIT	SPECIFICATION	DAILY
Manganese axial (SBR)	%	>100	433
Manganese radial (SBR)	%	>100	581
Rel. Stand. Deviation	%	≤ 3	0.51
Ratio axial Mg _{280.271} / Mg _{285.213}	---		5.37
Ratio radial Mg _{280.271} / Mg _{285.213}	---		7.60

The services described in this report are not covered by full validation for this specific sample matrix. Under no circumstances Intertek will be liable for any loss or damages, whether direct or indirect or any third-party claim, in relation to the applied method. If required, additional validation can be offered.

3.4 CFR 177.1520 (final products) samples

FDA extraction tests into n-hexane and Xylene as specified in USA FDA 21 CFR § 177.1520; *Olefin polymers*. The tests are performed in duplicate.

3.4.1 n-Hexane extraction test according to 21 CFR section 177.1520

A sample is extracted at for 2 hours at reflux temperature. The filtrate is evaporated, and the total residue weighed as a measure of the solvent extractable fraction. *Portions of approximately 1 gram were extracted with 100 ml n-hexane.*

3.4.2 Xylene soluble fraction test according to 21 CFR section 177.1520

The sample is dissolved completely in xylene by heating and stirring in a bottle with little free space. The solution is allowed to cool without stirring, whereupon the insoluble portion precipitates and is filtered off; the total solids content of the filtrate is then determined as a measure for the soluble fraction. *Portions of approximately 1 gram portions were extracted with 100 ml of xylene.*



RE36136-3A

September 1st, 2021

4 RESULTS AND DISCUSSION

4.1 TD GC-MS screening - volatiles

A numerous (non-)identified hydrocarbons and siloxanes have been detected. The results and chromatograms of the TD GC-MS analyses are presented in Appendix I; table 14 and figure 1 respectively.

Explanation of component identification using a commercial database:

- For the components with probability > 50%, the component name and the CAS number were provided;
- Probability takes into consideration the probable match and RI-index from the commercial database;
- If the probability is less (< 50%) the components were considered as unknowns without CAS numbers;
- If there is no match with the library the components were considered as unknowns. Unknowns can be further classified as likely to be, based on the main functional group or molecules present;
- If a spectrum does not match a component in the library but has a lot of similarity with a known component, the components were presented as unknowns with some info on the molecule;
- If a peak consists out of several components, the components were presented as Unknown + the number of components, e.g. Unknown 4x consists out of 4 unknown components;
- For unknowns, the three highest *m/z* masses were added to the component.

4.2 LC-MS screening – non-volatiles and additives

The results of the LC-MS screening to determine non-volatiles and additives are presented in table 9. Oleamide, Atmer 163, erucamide, hexadecanoic acid, octadecanoic acid, several Irgafos and Irganox substances have been identified.

Table 9: Results obtained from the LC-MS screening

RT (min)	COMPONENT	CAS	BLANK (MG/KG)	SAMPLE 3 INPUT 2021 PP PTT (MG/KG)	SAMPLE 3: 22 HR REFRESH OUTPUT MATERIAL 20-21 TRIAL(MG/KG)
0.86	Benzophenone	119-61-9	< 0.5	< 0.5	< 0.5
0.78	Irgacure 184	947-19-3	< 0.6	1.14	< 0.6
1.50	Oleamide	301-02-0	< 0.5	3.21	> 4.2 (4.8)
2.48	Atmer 163	-	< 0.5	> 5.1 (5.4)	> 5.1 (46)
4.67	Irganox PS800	53571-83-8	< 0.3	< 0.3	< 0.3
2.34	Erucamide	112-84-5	< 0.4	> 3.8 (15.2)	> 3.8 (27.4)
5.50	Irgafos 168	31570-04-4	< 0.3	> 0.7 (11.4)	> 0.7 (9.71)
6.08	Irganox PS802	693-36-7	< 0.4	4.10	9.03



RE36136-3A

September 1st, 2021

RT (min)	COMPONENT	CAS	BLANK (MG/KG)	SAMPLE 3 INPUT 2021 PP PTT (MG/KG)	SAMPLE 3: 22 HR REFRESH OUTPUT MATERIAL 20-21 TRIAL(MG/KG)
4.91	Irganox 1076	2082-79-3	< 2.0	< 2.0	< 2.0 (1.03)
5.13	Irgafos 168 ox	95906-11-9	< 0.3	> 11.6 (100)	> 7.9 (122)
1.25	Irganox 245	36443-68-2	< 0.6	< 0.6	1.01
5.61	Irganox 1010	6683-19-8	< 0.5	> 1.3 (46.3)	> 1.3 (60.9)
4.53	Irganox 3114	27676-62-6	< 0.3	3.79	4.04
1.70	Hexadecanoic acid	57-10-3	< 2.5	> 24.5 (114)	> 24.3 (128)
2.16	Octadecanoic acid	57-11-4	< 2.4	> 24.2 (70)	> 24.2 (102)
5.21	Irganox 1330	1709-70-2	< 0.5	1.27	1.29

The results of the chromatogram screening are presented in the appendix II; table 15 - 16 and Figure 2 - 3 respectively.



RE36136-3A

September 1st, 2021

4.3 Phthalates screening

The results of the phthalates screening are mentioned in table 10.

Table 10: Results for the phthalate screening

COMPONENT	COMPONENT	SAMPLE 3 INPUT 2021 PP SAMPLE (MG/KG)	SAMPLE 3: 22 HR REFRESH OUTPUT MATERIAL 20-21 TRIAL (MG/KG)
Bis(2-ethylhexyl) phthalate	DEHP	< 0.05	0.11
Diisononyl phthalate	DINP	< 0.10	< 0.10
Benzylbutylphthalat	BBP	< 0.10	< 0.10
Dibutylphthalate en Diisobutylphthalate	DBP en DIBP	0.59	0.16
Diethylphthalate	DEP	0.20	< 0.10
Dimethyl phthalate	DMP	< 0.05	< 0.05
Di-n-hexyl phthalate	DNHP	< 0.10	< 0.10
Dipentyl phthalate	DPP	< 0.05	< 0.05
Di-isohexyl phthalate (DIHxP)	DIHxP	< 0.10	< 0.10
Di n octyl phthalate	DnOP	< 0.10	< 0.10
Dinonyl phthalate (DNP)	DNP	< 0.05	< 0.05
Diisopentyl phthalate	DIPP	< 0.05	< 0.05
Diisodecyl phthalate (DIDP)	DIDP	< 0.50	< 0.50



RE36136-3A

September 1st, 2021

4.3 Metal screening (ICP/MS, FIMS): screening multi-elements

The results of the elemental analysis by means of ICP-OES/ICP-MS and FIMS are mentioned in table 11 and are expressed as mg/kg material.

Table 11: Results elemental analysis

Element	Sample 3 Input 2021 PP Sample (mg/kg)	Sample 3: 22 hr refresh output material 20-21 trial (mg/kg)
Ag	0.03	0.05
Al	1000	160
As	< 0.14	< 0.14
B	3.52	< 0.4
Ba	12.2	23.4
Be	< 0.03	< 0.03
Bi	< 0.4	< 0.4
Cd	< 0.02	< 0.02
Ce	0.11	0.80
Co	< 0.8	< 0.8
Cr	22.3	4.99
Cs	1.97	3.05
Cu	3.13	1.97
Fe	145	49.1
In	< 0.4	< 0.4
Mn	2.63	0.84
Mo	0.31	0.11
Ni	9.64	2.46
Pb	0.32	0.24
Rb	< 0.4	< 0.4
Sb	0.92	1.66
Se	< 0.1	< 0.1
Si	220	175
Sn	< 0.7	< 0.7
Sr	0.88	1.79
Th	< 0.2	< 0.2
Ti	320	210
Tl	< 0.05	< 0.05
U	< 0.04	< 0.04
V	0.23	0.15
W	< 0.4	< 0.4
Zn	21.5	21.9
Zr	1.37	0.98



RE36136-3A

September 1st, 2021

4.4 CFR 177.1520 (final products) samples

4.4.1 Maximum extractable fraction in n-hexane

The results of the maximum extractable fraction in n-hexane are mentioned in table 12 and are expressed as a percentage by weight of the polymer.

Start date test: July 21st, 2021.

Table 12: Results maximum extractable fraction in n-hexane

SAMPLE	MAXIMUM EXTRACTABLE FRACTION IN N-HEXANE AT REFLUX TEMPERATURE			
	REP 1 (%)	REP 2 (%)	MEAN (%)	SPECIFICATION § 177.1520 (%)
Sample 3: 22 hr refresh output material 20-21 trial	0.95	0.95	1.0	6.4

4.4.2 Maximum soluble fraction in xylene

The results of the maximum soluble fraction in xylene are mentioned in table 13 and are expressed as a percentage by weight of the polymer.

Start date test: July 21st, 2021.

Table 13: Results maximum soluble fraction in xylene

SAMPLE	MAXIMUM SOLUBLE FRACTION IN XYLENE AT 25°C			
	REP 1 (%)	REP 2 (%)	MEAN (%)	SPECIFICATION § 177.1520 (%)
Sample 3: 22 hr refresh output material 20-21 trial	10.41	11.56	11.0	9.8

4.4.2.1 Re-analysis of Maximum soluble fraction in xylene

The results of the maximum soluble fraction in xylene are mentioned in table 13-1 and are expressed as a percentage by weight of the polymer.

Start date test: August 27th, 2021.

Table 13-1: Results maximum soluble fraction in xylene (re-analysis)

SAMPLE	MAXIMUM SOLUBLE FRACTION IN XYLENE AT 25°C			
	REP 1 (%)	REP 2 (%)	MEAN (%)	SPECIFICATION § 177.1520 (%)
Sample 3: 22 hr refresh output material 20-21 trial	9.95	10.18	10.1	9.8



RE36136-3A

September 1st, 2021

APPENDIX I: RESULTS AND CHROMATOGRAMS OF TD GC-MS SCREENING

Table 14: Results of the TD GC-MS screening

RT (MIN)	COMPONENT	CAS	CONCENTRATION IN MATERIAL (MG/KG)	
			INPUT	OUTPUT
8.61	Acetone	67-64-1	1.6	<0.1
8.94	Isopropyl Alcohol	67-63-0	0.2	<0.1
9.61	Pentane, 2-methyl-	107-83-5	0.2	0.1
9.73	2-Propanol, 2-methyl-	75-65-0	0.2	0.1
11.46	Propane, 2-ethoxy-2-methyl-	637-92-3	0.1	<0.1
11.51	Silanol, trimethyl-	1066-40-6	0.1	<0.1
11.61	Cyclopentane, methyl-	96-37-7	0.1	<0.1
11.71	2-Butanone	78-93-3	0.1	<0.1
13.09	Benzene	71-43-2	0.2	<0.1
13.78	1-Butanol	71-36-3	0.9	<0.1
14.37	Hexane, 2,4-dimethyl-	589-43-5	0.2	0.2
14.75	2-Butanone, 3,3-dimethyl-	75-97-8	0.2	<0.1
15.23	Heptane, 4-methyl-	589-53-7	0.3	0.2
15.9	Toluene	108-88-3	2.6	<0.1
16.44	Hexane, 2,3,5-trimethyl-	1069-53-0	0.6	0.4
16.55	Heptane, 2,4-dimethyl-	2213-23-2	4.5	3.4
16.91	Unknown Branched Alkene (m/z 83, 56, 55)		0.1	<0.1
16.95	Hexanal	66-25-1	<0.1	0.1
17.09	Unknown Branched Alkene (m/z 70, 43, 55)		1.4	1.1
17.37	Heptane, 2,3-dimethyl-	3074-71-3	0.4	0.3
17.46	Octane, 4-methyl-	2216-34-4	1.4	1.2
17.71	4,4-Dimethyl octane	15869-95-1	0.1	<0.1
18.22	Unknown Branched Alkane (m/z 43, 69, 83)		0.1	0.1
18.76	3-Heptanone	106-35-4	0.1	<0.1
19.4	α -Pinene	80-56-8	0.2	0.4
19.76	Unknown Branched Alkane (m/z 57, 43, 85)		1.0	0.5
19.87	Camphene	79-92-5	<0.1	0.1
19.98	3-Phenylpropionic acid, 4-cyanophenyl ester	no cas	0.1	0.1

This test report, including front-page and attachments, shall not be reproduced except in full, without written approval of Intertek Polychemlab B.V.
 This version replaces all previous versions.



RE36136-3A

 September 1st, 2021

RT (MIN)	COMPONENT	CAS	CONCENTRATION IN MATERIAL (MG/KG)	
			INPUT	OUTPUT
20.19	Decane	124-18-5	<0.1	0.5
20.28	Unknown Branched Alkane (m/z 57, 56, 41)		0.6	0.4
20.39	Unknown Branched Alkane (m/z 71, 57, 43)		1.0	0.5
20.46	Unknown Branched Alkane (m/z 71, 57, 43)		1.1	0.8
20.56	Unknown Branched Alkane (m/z 57, 43, 85)		0.2	0.2
20.62	Unknown Branched Alkane (m/z 71, 57, 43)		0.4	0.3
20.73	Unknown Branched Alkene (m/z 56, 70, 85)		0.2	0.1
20.86	Benzaldehyde	100-52-7	0.1	0.3
21.05	7-Oxabicyclo[2.2.1]heptane, 1-methyl-4-(1-methylethyl)-	470-67-7	0.2	0.2
21.23	Unknown Branched Alkane (m/z 71, 57, 43)		1.8	2.9
21.27	Unknown Branched Alkane (m/z 71, 57, 85)		15.7	12.2
21.38	Unknown Branched Alkane (m/z 71, 57, 85)		4.9	3.3
21.53	1-Hexanol, 2-ethyl-	104-76-7	7.7	0.5
21.76	Unknown Branched Alkene (m/z 69, 70, 71)		1.6	0.8
21.83	Unknown Branched Alkene (m/z 69, 70, 83)		0.9	0.6
22	Unknown Branched Alkane (m/z 71, 57, 85)		1.0	1.0
22.03	Undecane	1120-21-4	8.1	6.1
22.13	Unknown Branched Alkane (m/z 71, 57, 43)		2.6	2.2
22.25	Unknown Branched Alkane (m/z 71, 43, 57)		1.4	2.1
22.26	Unknown Branched Alkane (m/z 71, 57, 43)		0.7	1.3
22.59	Unknown Ester (m/z 111, 43, 84)		0.1	0.1
22.63	Unknown Branched Alkene (m/z 73, 58, 43)		0.2	0.2
22.72	Linalool	78-70-6	0.2	0.2
22.84	Nonanal	124-19-6	0.2	0.9
22.91	Unknown Branched Alkane (m/z 57, 112, 84)		0.1	0.4
22.98	Unknown Branched Alkane (m/z 71, 43, 85)		0.1	0.4
23.01	trans-Decalin, 2-methyl-	-	0.1	0.1
23.05	Unknown Branched Alkane (m/z 71, 43, 57)		0.1	0.2
23.18	Unknown Branched Alkane (m/z 57, 71, 85)		0.1	0.4
23.24	Unknown Branched Alkane (m/z 57, 71, 85)		0.1	0.1
23.33	Unknown decahydronaphthalene (m/z 152, 95, 69)		0.2	<0.1

This test report, including front-page and attachments, shall not be reproduced except in full, without written approval of Intertek Polychemlab B.V.
 This version replaces all previous versions.



RE36136-3A

 September 1st, 2021

RT (MIN)	COMPONENT	CAS	CONCENTRATION IN MATERIAL (MG/KG)	
			INPUT	OUTPUT
23.42	Unknown Cyclohexanone (m/z 105, 152, 95)		0.1	<0.1
23.58	Fenchol	1632-73-1	0.2	0.2
23.62	Dodecane	112-40-3	0.4	0.8
23.7	Unknown Branched Alkane (m/z 57, 71, 85)		0.1	0.1
23.72	Unknown Branched Alkane (m/z 57, 71, 85)		0.4	0.4
23.84	Unknown Branched Alkane (m/z 57, 71, 43)		0.3	0.2
23.91	Unknown Branched Alkane (m/z 57, 71, 43)		0.2	0.1
23.93	Unknown Ester (m/z 125, 57, 56)		0.1	<0.1
24.22	Unknown Branched Alkane (m/z 71, 57, 43)		0.2	0.1
24.35	Unknown Branched Alkane (m/z 71, 57, 43)		0.5	0.5
24.39	Unknown Cyclohexanol (m/z 57, 71, 95)		0.6	0.3
24.47	Unknown Branched Alkane (m/z 71, 57, 85)		0.4	0.9
24.64	α -Terpineol	98-55-5	1.0	1.4
24.75	Unknown Branched Alkane (m/z 57, 71, 56)		0.1	<0.1
24.89	Unknown Branched Alkane (m/z 71, 57, 85)		14.1	14.7
25.02	Unknown Branched Alkane (m/z 71, 57, 85)		2.0	2.3
25.11	Unknown Branched Alkane (m/z 71, 57, 85)		1.2	1.2
25.23	Unknown Branched Alkane (m/z 71, 57, 85)		1.3	1.6
25.38	Unknown Branched Alkene (m/z 69, 83, 111)		1.2	1.3
25.5	Unknown Branched Alkene (m/z 69, 83, 111)		1.1	1.1
25.55	Unknown Branched Alkane (m/z 71, 57, 85)		8.2	9.0
25.63	Unknown Branched Alkene (m/z 69, 85, 57)		1.2	1.4
25.69	Unknown Branched Alkane (m/z 71, 57, 85)		1.9	2.3
25.81	Unknown Branched Alkane (m/z 71, 57, 85)		2.0	2.2
25.83	Unknown Branched Alkane (m/z 71, 57, 85)		0.7	1.1
25.94	Unknown Branched Alkane (m/z 57, 71, 85)		1.0	1.5
26.02	Unknown Cyclohexanol (m/z 82, 67, 57)		0.1	1.3
26.03	Unknown Cyclohexanol (m/z 82, 67, 123)		0.1	1.1
26.21	Unknown Cyclohexane (m/z 82, 83, 57)		0.4	0.2
26.29	Unknown Branched Alkane (m/z 71, 57, 85)		0.7	0.1
26.31	Unknown Branched Alkane (m/z 71, 57, 85)		0.1	0.2
26.4	4,7-Methano-1H-indenol, hexahydro-	37275-49-3	0.2	0.1

This test report, including front-page and attachments, shall not be reproduced except in full, without written approval of Intertek Polychemlab B.V.
This version replaces all previous versions.



RE36136-3A

 September 1st, 2021

RT (MIN)	COMPONENT	CAS	CONCENTRATION IN MATERIAL (MG/KG)	
			INPUT	OUTPUT
26.58	Tetradecane	629-59-4	2.0	2.0
26.68	a-Terpinyl acetate	80-26-2	<0.1	0.5
26.92	Unknown Branched Alkane (m/z 57, 71, 85)		0.3	0.6
26.96	Unknown Branched Alkane (m/z 85, 57, 71)		<0.1	0.1
27.08	Unknown Cycloalkane (m/z 97, 96, 55)		<0.1	0.8
27.11	Unknown Branched Alkane (m/z 57, 85, 71)		<0.1	0.3
27.38	Unknown Branched Alkane (m/z 71, 57, 43)		0.1	0.2
27.44	Unknown Branched Alkane (m/z 71, 57, 85)		1.1	1.1
27.46	Unknown Branched Alkane (m/z 71, 57, 85)		0.4	0.4
27.51	Unknown Branched Alkane (m/z 57, 85, 71)		0.2	0.4
27.58	Unknown Branched Alkane (m/z 57, 71, 85)		0.2	0.2
27.81	Unknown Ester (m/z 57, 85, 71)		0.1	0.2
27.83	Unknown Branched Alkane (m/z 71, 57, 85)		0.3	0.4
27.93	Unknown Branched Alkane (m/z 71, 85, 57)		14.8	18.7
28.05	Unknown Branched Alkane (m/z 71, 57, 85)		2.1	3.8
28.13	Unknown Branched Alkane (m/z 58, 71, 85)		0.9	3.6
28.25	Unknown Cycloalkane (m/z 58, 83, 55)		0.7	0.2
28.27	Unknown Branched Alkane (m/z 58, 83, 69)		0.3	0.1
28.38	Unknown Ester (m/z 71, 57, 69)		1.4	3.6
28.49	Unknown Branched Alkane (m/z 71, 85, 57)		9.8	12.7
28.61	Unknown Branched Alkane (m/z 71, 57, 85)		2.4	3.3
28.73	Unknown Branched Alkane (m/z 71, 57, 85)		2.4	3.8
28.86	Unknown Branched Alkane (m/z 71, 57, 85)		1.5	2.2
28.88	Unknown Branched Alkane (m/z 71, 57, 85)		0.8	1.0
29	Unknown Branched Alkane (m/z 71, 57, 85)		0.9	1.2
29.07	Unknown Branched Alkane (m/z 71, 57, 85)		0.1	0.2
29.16	Unknown Acid (m/z 191, 57, 206)		0.3	2.6
29.19	Hexadecane	544-76-3	1.8	1.9
29.48	Unknown (m/z 99, 83, 98)		<0.1	0.1
29.54	Unknown Cycloalkane (m/z 97, 55, 83)		0.1	0.3
29.7	Unknown Branched Alkane (m/z 71, 57, 85)		0.2	0.4
29.75	Unknown Branched Alkane (m/z 57, 71, 105)		0.4	1.9

This test report, including front-page and attachments, shall not be reproduced except in full, without written approval of Intertek Polychemlab B.V.
This version replaces all previous versions.



RE36136-3A

 September 1st, 2021

RT (MIN)	COMPONENT	CAS	CONCENTRATION IN MATERIAL (MG/KG)	
			INPUT	OUTPUT
29.76	Unknown Branched Alkane (m/z 57, 71, 85)		0.3	0.5
29.96	Benzene, (1-pentylhexyl)-	4537-14-8	0.1	1.2
30.01	Benzene, (1-butylheptyl)-	4537-15-9	0.1	1.0
30.07	Octane, 1,1'-oxybis-	629-82-3	0.5	0.5
30.18	Benzene, (1-propyloctyl)-	4536-86-1	0.4	0.5
30.27	Unknown Branched Alkane (m/z 57, 71, 85)		0.5	0.4
30.39	Unknown Branched Alkane (m/z 57, 71, 85)		0.9	2.8
30.61	Unknown Branched Alkane (m/z 71, 85, 57)		14.8	17.3
30.71	Unknown Branched Alkane (m/z 71, 85, 57)		2.1	2.7
30.78	Unknown Ester (m/z 71, 57, 85)		0.9	0.6
31.07	Unknown Alkene (m/z 69, 57, 111)		0.7	0.9
31.14	Unknown Branched Alkane (m/z 71, 85, 57)		7.1	9.0
31.18	Unknown Branched Alkane (m/z 71, 57, 85)		1.1	1.3
31.25	Unknown Branched Alkane (m/z 71, 57, 85)		2.0	2.3
31.34	Benzophenone	119-61-9	0.4	2.9
31.41	Unknown Ester (m/z 71, 57, 69)		0.8	1.0
31.51	Unknown Branched Alkane (m/z 71, 57, 85)		0.3	0.3
31.54	Unknown Ether (m/z 69, 71, 111)		0.3	0.4
31.57	Amberonne (isomer 2)	-	0.5	1.0
31.67	Unknown Branched Alkane (m/z 57, 71, 85)		1.3	1.4
31.83	Unknown Ether (m/z 71, 57, 69)		0.5	0.8
31.97	Unknown Branched Alkane (m/z 71, 57, 85)		0.3	0.6
32.12	Amberonne (isomer 3)	-	0.1	0.3
32.35	Isopropyl myristate	110-27-0	0.1	4.0
32.43	Octanal, 2-(phenylmethylene)-	101-86-0	0.1	1.5
32.5	Unknown Branched Alkane (m/z 91, 71, 57)		0.2	0.5
32.63	Benzene, (1-butylnonyl)-	4534-50-3	0.1	0.1
32.74	Cyclohexyl salicylate	-	<0.1	0.7
32.99	Unknown Branched Alkane (m/z 71, 57, 85)		0.3	0.5
33.1	Unknown Branched Alkane (m/z 57, 71, 85)		0.2	0.4
33.14	2-Ethylhexyl salicylate	118-60-5	0.2	1.1
33.19	3,5-di-tert-Butyl-4-hydroxybenzaldehyde	1620-98-0	0.1	0.4

This test report, including front-page and attachments, shall not be reproduced except in full, without written approval of Intertek Polychemlab B.V.
 This version replaces all previous versions.



RE36136-3A

September 1st, 2021

RT (MIN)	COMPONENT	CAS	CONCENTRATION IN MATERIAL (MG/KG)	
			INPUT	OUTPUT
33.41	Benzene, 1,1'-[1,2-ethanediylbis(oxy)]bis-	104-66-5	0.2	0.2
33.6	Unknown Branched Alkane (m/z 71, 85, 57)		8.4	11.1
33.69	Unknown Branched Alkane (m/z 71, 57, 85)		2.5	2.8
33.75	Unknown Branched Alkane (m/z 71, 57, 85)		0.4	0.8
33.99	Cyclopenta[g]-2-benzopyran, 1,3,4,6,7,8-hexahydro-4,6,6,7,8,8-hexamethyl-	1222-05-5	0.2	0.7
34.17	Unknown Branched Alkane (m/z 71, 57, 69)		0.1	0.1
34.22	Unknown Branched Alkane (m/z 71, 57, 85)		0.4	0.6
34.26	Unknown Branched Alkane (m/z 71, 85, 57)		3.6	5.1
34.38	Unknown Branched Alkane (m/z 71, 57, 85)		1.3	1.7
34.54	Unknown Branched Alkane (m/z 71, 85, 57)		0.1	0.1
34.72	Eicosane	112-95-8	0.4	0.6
34.89	Unknown Branched Alkane (m/z 71, 85, 57)		0.1	0.1
34.93	Homosalate	118-56-9	<0.1	0.3
35.03	Unknown Branched Alkane (m/z 71, 85, 57)		0.2	0.2
35.21	Unknown Aromate (m/z 178, 194, 179)		0.2	0.4
35.39	Unknown Branched Alkane (m/z 99, 57, 112)		0.2	<0.1
35.62	Isopropyl palmitate	142-91-6	<0.1	0.9
35.79	Unknown Branched Alkane (m/z 71, 57, 85)		0.1	0.1
36	Unknown Phthalic acid (m/z 149, 73, 57)		<0.1	0.2
36.94	7,9-Di-tert-butyl-1-oxaspiro(4,5)deca-6,9-diene-2,8-dione	82304-66-3	0.4	3.0
37.67	Unknown Branched Alkane (m/z 71, 85, 57)		3.1	4.3
37.82	Unknown Branched Alkane (m/z 71, 85, 57)		0.4	0.5
38.02	Diphenyl sulfone	127-63-9	0.4	0.1
38.42	Unknown Branched Alkane (m/z 71, 85, 57)		0.1	0.2
38.62	Unknown Branched Alkane (m/z 71, 85, 57)		1.1	1.7
38.8	Unknown Branched Alkane (m/z 71, 85, 57)		0.2	0.3
39.01	Unknown Branched Alkane (m/z 57, 71, 85)		0.1	0.1
39.21	Unknown Fatty Acid Ester (m/z 71, 57, 85)		<0.1	0.1

This test report, including front-page and attachments, shall not be reproduced except in full, without written approval of Intertek Polychemlab B.V.
 This version replaces all previous versions.



RE36136-3A
September 1st, 2021

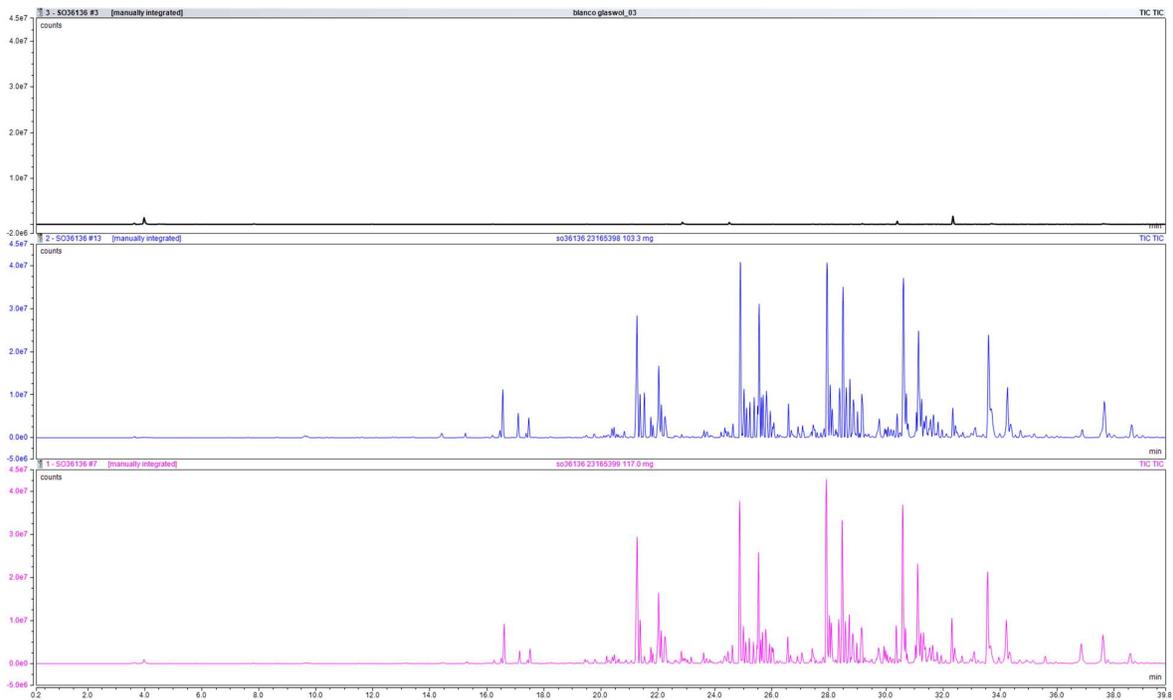


Figure 1: Screening of volatile components from the samples: Sample 3 Input 2021 PP Sample and Sample 3: 22 hr refresh output material 20-21 trial. Top trace is the blank chromatogram, the blue trace is the chromatograms of the input and the pink trace is the chromatogram of the output.



RE36136-3A
September 1st, 2021

APPENDIX II: RESULTS AND CHROMATOGRAMS OF LC-MS SCREENING

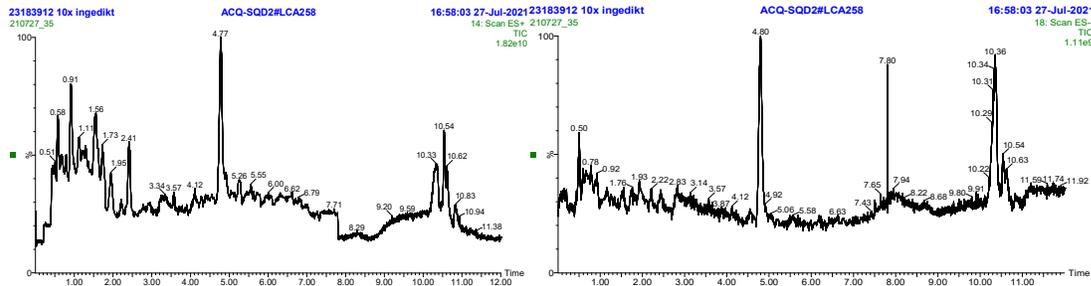


Figure 2: Chromatogram of Sample 3 input 2021 PP ptt

Table 15: Screening of unknowns, Sample 3 input 2021 PP ptt

RT	M/Z	COMPONENT	ESI MODE
0.58	275, 288.73, 316.75	Unknown	Positive
0.91	433 / 847	Unknown	Positive
1.56	503	Unknown	Positive
10.33	771 / 839.4	Unknown	Positive
10.54	161.4 / 189.43	Unknown	Positive
10.62	145.42 / 177.32	Unknown	Positive
4.8	205 / 1099		Negative
10.36	181 / 249 / 317		Negative

This test report, including front-page and attachments, shall not be reproduced except in full, without written approval of Intertek Polychemlab B.V.
This version replaces all previous versions.



RE36136-3A
September 1st, 2021

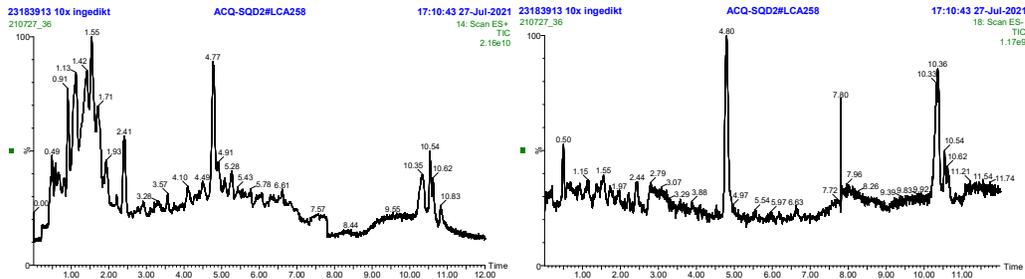


Figure 3: Chromatogram of Sample 3: 22 hr refresh output material 20-21 trial, left ESI+ , right ESI-

Table 516: Screening of unknowns, Sample 3: 22 hr refresh output material 20-21 trial.

RT	M/Z	COMPONENT	ESI MODE
0.49	145	Unknown	Positive
0.91	433 / 847	Unknown	Positive
1.13	396/ 441 / 485	Unknown	Positive
1.42	395 / 439 / 483	Unknown	Positive
1.71	467/ 555/ 599	Unknown	Positive
1.93	310 / 381	Unknown	Positive
3.57	395	Unknown	Positive
4.1	538	Unknown	Positive
4.49	566 / 723	Unknown	Positive
4.77	495.2 / 663.4	Unknown	Positive
5.28	615 / 691	Unknown	Positive
6.61	227 / 295	Unknown	Positive
10.35	567 / 704 / 839	Unknown	Positive
10.54	161.4 / 189.43	Unknown	Positive
10.62	145.42 / 204	Unknown	Positive
10.83	162 / 221	Unknown	Positive
4.8	205 / 1099	Unknown	Negative
10.36	181 / 249 / 317	Unknown	Negative

